If you do not need this publication after it has served your purpose, please return it to the Geological Survey, using the official mailing label at the end

UNITED STATES DEPARTMENT OF THE INTERIOR
Harold L. Ickes, Secretary

GEOLOGICAL SURVEY
W. C. Mendenhall, Director

Bulletin 897—D

BUREAU OF MINES
ANCHORAGE, ALASKA
AUG 15 1950
RECEIVED

NICKEL CONTENT OF AN ALASKAN BASIC ROCK

BY

JOHN C. REED

Mineral resources of Alaska, 1936
(Pages 263–268)

UNITED STATES
GOVERNMENT PRINTING OFFICE
WASHINGTON : 1939

For sale by the Superintendent of Documents, Washington, D. C. - - - - - - - - Price 5 cents

CONTENTS

	Page
Abstract	263
Location and general features	263
Petrographic studies	265
Chemical analyses	267
Conclusions	268

ILLUSTRATION

	Page
FIGURE 11. Index map showing location of nickel-bearing sill on Admiralty Island	264

NICKEL CONTENT OF AN ALASKAN BASIC ROCK

By John C. Reed

ABSTRACT

A nickel-bearing sill, about 126 feet thick, lies in a thick sequence of greenstone schists, graphitic phyllites, and quartzites near the north end of Admiralty Island not far from Juneau, Alaska.

Petrographic measurements show that volumetrically the rock is made up of about 62.07 percent labradorite, 34.22 percent olivine, 2.42 percent pyroxene, 0.79 percent pyrrhotite, 0.21 percent magnetite, 0.14 percent chalcopyrite, and 0.06 percent pentlandite.

By weight the rock contains about 0.20 percent chalopyrite and 0.10 percent pentlandite. The copper content in chalcopyrite therefore is about 0.067 percent and the nickel content in pentlandite about 0.025 percent.

Chemical analyses of representative samples show the rock as a whole to contain about 0.350 percent copper and 0.344 percent nickel. The differences between the petrographic and the chemical results are believed to be due only in part to the fact that the few thin and polished sections studied may not be representative of the rock. The large differences appear to indicate that much of the nickel is present in the rock in some other mineral than pentlandite, presumably in olivine.

LOCATION AND GENERAL FEATURES

Several nickel-bearing deposits are known in southeastern Alaska,[1] although no significant quantities of nickel have been produced from Alaskan ores. The deposits have many features in common and are similar to many nickel-bearing deposits throughout the world.

This paper deals with a nickel-bearing sill known at the outcrop as the "Mertie lode," near the north end of Admiralty Island (fig. 11) not far from Juneau.

The country rocks of the vicinity comprise a thick sequence of greenstone schists, graphitic phyllites, and quartzites and several bodies of diorite or gabbro. The principal structural feature of the area is a large anticline that pitches about 30° SE. The nickel-bearing sill lies high on the anticline but somewhat to the east of its apparent axis. Outcrops near the sill are poor, and the only natural

[1] Overbeck, R. M., Geology and mineral resources of the west coast of Chichagof Island: U. S. Geol. Survey Bull. 692, pp. 125–133, 1919. Kerr, P. F., A magmatic sulphide ore from Chichagof Island, Alaska: Econ. Geology, vol. 19, pp. 369–376, 1924. Buddington, A. F., Alaskan nickel minerals: Econ. Geology, vol. 19, pp. 521–541, 1924; Mineral investigations in southeastern Alaska: U. S. Geol. Survey Bull. 773, pp. 95–113, 1925; Mineral investigations in southeastern Alaska: U. S. Geol. Survey Bull. 783, p. 46, 1926. Buddington, A. F., and Chapin, Theodore, Geology and mineral deposits of southeastern Alaska: U. S. Geol. Survey Bull. 800, pp. 348–351, 1929.

exposures are an outcrop along a small stream and another very small outcrop about 40 feet east of the stream. The deposit has been prospected by a tunnel 110 feet long and by several diamond-drill holes.

At the outcrop along the stream the hanging wall is light-colored siliceous schist, about 20 feet thick, overlain by graphitic phyllite. The footwall is greenstone schist.

The sill is about 126 feet thick, strikes N. 15° W., and dips 38° E. The rock is very dark, almost black, coarse grained, and contains

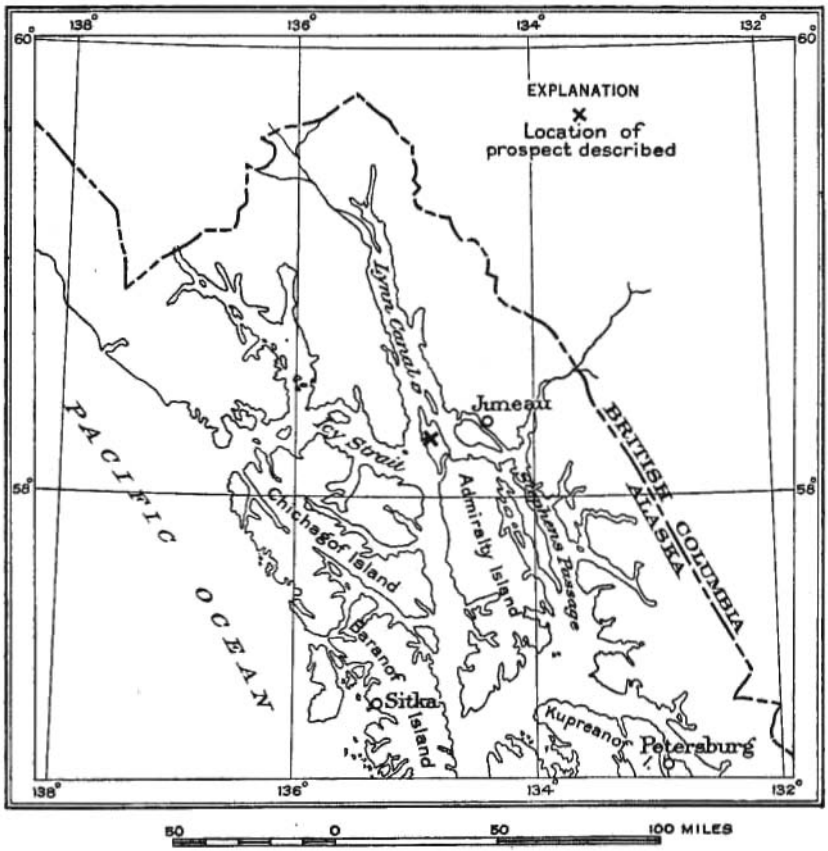

FIGURE 11.—Index map showing location of nickel-bearing sill on Admiralty Island.

sporadic finer-grained masses as much as several inches across. Numerous joints cut the rock in the tunnel. These joints trend about N. 10° E. and dip about 50° W. Many of them form channels for the passage of water, and near the face are filled with as much as an inch of hydrated oxides of iron. Near the portal the joints are very conspicuous, and some of them contain several inches of limonite. Also near the portal weathering has spread widely from the joints

and has produced characteristic boulderlike forms. The weathered rock is stained with limonite. Careful examination of the rock in the tunnel failed to reveal any flow bands or any finer-grained border rock near the footwall, the only wall exposed in the tunnel. The absence of fine-grained chilled borders and the coarse grain of the rock suggest that the sill may be only a small part of a much larger body.

PETROGRAPHIC STUDIES

The rock of the sill has been classified by Buddington as troctolite. Buddington[2] found the rock to contain 55 percent labradorite, 39 percent olivine, 4 percent pyroxene, and 2 percent magnetite.

This paper is largely based on the study of five thin sections and three polished sections cut from the sill. Three of the thin sections are from material collected by Buddington.

The secondary minerals comprise a complex assemblage that includes sericite, carbonates, brown hornblende, serpentine, talc, biotite, and chlorite. The opaque minerals include magnetite, ilmenite, pyrrhotite, chalcopyrite, and pentlandite.

The approximate mineral constitution of the rock at each of the places from which a thin section was available was determined by making about six measured traverses in different directions across each thin section. From these were calculated the volumetric proportions of plagioclase, olivine, pyroxene, combined alteration products, and combined opaque minerals given in the table below.

Volumetric percentages of principal constituents, alteration products, and opaque minerals of specimens from a sill on Admiralty Island

Specimen	Plagioclase	Olivine	Pyroxene	Alteration products	Opaque minerals	Total
A	37.1	18.4	2.5	30.0	11.7	99.7
B	62.8	30.0	2.6	3.4	1.0	99.8
C	66.9	6.7	1.3	24.1	1.0	100.0
D	53.5	32.2	2.6	10.0	1.6	99.9
E	29.0	29.7	13.5	9.6	18.3	100.1
Average of B, C, and D	61.07	22.97	2.17	12.50	1.20	99.91

Specimen E was collected from the part of the lode richest in sulphides, so far as seen. It was therefore not used in calculating the average constitution of the sill. Similarly specimen A, which was collected by Buddington, was left out of the same calculation because it contains a far larger proportion of opaque minerals than the average rock. The remaining specimens, B, C, and D, were then averaged to reach an approximation of the average rock of the sill as exposed and as represented by the thin sections.

[2] Buddington, A. F., Mineral investigations in southeastern Alaska: U. S. Geol. Survey Bull. 783, p. 46, 1926.

It was estimated from the study of the thin sections that about 90 percent of the alteration products were formed at the expense of olivine, about 8 percent at the expense of plagioclase, and about 2 percent at the expense of pyroxene. The alteration minerals were then assigned to the plagioclase, olivine, and pyroxene in proportion to the estimated ratios, and the original constitution of the average rock, as represented by specimens B, C, and D, was calculated. Similarly the original constitutions of the rocks represented by specimens A and E, were calculated as shown in the following table.

Original volumetric percentages of principal constituents and combined opaque minerals of specimens from a sill on Admiralty Island

Specimen	Plagioclase	Olivine	Pyroxene	Opaque minerals	Total
A	39.5	45.4	3.1	11.7	99.7
Average of B, C, and D	62.07	34.22	2.42	1.20	99.91
E	29.8	38.3	13.7	18.3	100.1

Traverses were next made across the three polished sections, and the approximate relative volumetric proportions of pyrrhotite, magnetite, chalcopyrite, and pentlandite were determined for each of the sections as shown below.

Volumetric percentage of combined opaque minerals furnished by each opaque mineral in specimens from a sill on Admiralty Island

Polished section	Pyrrhotite	Magnetite	Chalcopyrite	Pentlandite	Total
1	80.1	5.1	9.5	5.2	99.9
2	63.6	12.9	15.9	7.5	99.9
3	54.8	33.2	8.8	3.2	100.0
Average	66.2	17.1	11.4	5.3	100.0

The average percentage of each opaque mineral among the combined opaque minerals was assumed to hold for the sill as a whole and was then used in calculating the volumetric percentage of each opaque mineral in specimens A and E and in the average of B, C, and D from the percentage of combined opaque minerals that had already been determined. (See table below.)

Volumetric percentages of minerals from specimens of a sill on Admiralty Island

Specimen	Plagioclase	Olivine	Pyroxene	Pyrrhotite	Magnetite	Chalcopyrite	Pentlandite	Total
A	39.5	45.4	3.1	7.75	2.00	1.33	0.62	99.7
Average of B, C, and D	62.07	34.22	2.42	0.79	0.21	0.14	0.06	99.91
E	29.8	38.3	13.7	12.11	3.13	2.09	0.97	100.1

The volumetric percentages of the chalcopyrite and of the pentlandite in the average rock (average of specimens B, C, and D) were then converted into percentages by weight. In the calculations the following specific gravities of the minerals were used: For labradorite, 2.7; for olivine, 3.5; for pyroxene, 3.4; for pyrrhotite, 4.6; for magnetite, 5.2; for chalcopyrite, 4.2; and for pentlandite, 5.0. The specific gravity of the average rock may be about 3 and the rock may carry about 0.20 percent chalcopyrite and 0.10 percent pentlandite by weight.

Chalcopyrite contains about 34.5 percent copper, and the average rock of the sill, with 0.20 percent chalcopyrite, should therefore contain in chalcopyrite 0.067 percent copper. The composition of pentlandite is not fixed, but A. H. Phillips analyzed pentlandite from Yakobi Island in southeastern Alaska for Buddington [3] and found it to contain 24.65 percent nickel. If this amount approximates the nickel content of the pentlandite from the sill on Admiralty Island, the sill may contain in pentlandite about 0.025 percent nickel. The rock therefore may carry in these two sulphides about 2¾ times as much copper as nickel.

CHEMICAL ANALYSES

The table following lists the results of chemical analyses made by R. C. Wells of six samples taken from the 110-foot prospect tunnel.

Percentages of copper and nickel in samples from a sill on Admiralty Island

	1	2	3	4	5	6
Copper	0.26	0.27	0.36	0.25	0.61	0.45
Nickel	.28	.24	.34	.25	.61	.30

1. Chip sample along the inner 28 feet of the tunnel.
2. Channel sample from 6-foot vertical cut at center of tunnel face.
3. Channel sample from 7-foot vertical cut on right side of tunnel, 100 feet from the portal.
4. Channel sample from 7-foot vertical cut on left side, 100 feet from the portal.
5. Channel sample from 7-foot vertical cut on right side, 75 feet from portal.
6. Channel sample from 7-foot vertical cut on right side, 39 feet from portal.

Sample 6 in the table above was cut from weathered material to find out if weathering produced any notable differences in the amounts or proportions of copper and nickel present.

The average content of copper and nickel in the rock as a whole as exposed in the prospect tunnel is probably closely approximated in the averages for each metal in the samples above. The values for sample 6 are omitted from the calculations because sample 6 was weathered material. Thus the average rock probably contains about 0.350 percent copper and 0.344 percent nickel.

[3] Buddington, A. F., Alaskan nickel minerals: Econ. Geology, vol. 19, p. 523, 1924.

CONTENTS

[The letters in parentheses preceding the titles are those used to designate the papers for separate publication]

	Page
(A) Mineral industry of Alaska in 1936, by P. S. Smith (published in March 1938)	1
(B) The Valdez Creek mining district in 1936, by Ralph Tuck (published in March 1938)	109
(C) Gold placers of the Fortymile, Eagle, and Circle districts, by J. B. Mertie, Jr. (published in August 1938)	133
(D) Nickel content of an Alaskan basic rock, by J. C. Reed (published in May 1939)	263
Selected list of Geological survey publications on Alaska	On back of plate 1

ILLUSTRATIONS

	Page
PLATE 1. Map of Alaska, showing areas covered by selected available reports and maps of Alaska	In pocket
2. Sketch map of Fortymile district, showing location of gold placer-mining operations	160
3. Sketch map of Eagle district, showing location of gold placer-mining operations	192
4. Sketch map of Circle district, showing location of gold placer-mining operations	208
5. Sketch map showing location of placer-mining claims on Coal Creek, Circle district	250
6. Sketch map showing location of placer-mining claims on Woodchopper Creek, Circle district	256
FIGURE 1. Trends of mineral production of Alaska, 1890–1936	8
2. Trend of value of gold production of Alaska, 1880–1936	12
3. Sketch map of Nuka Bay and vicinity	25
4. Copper produced from Alaska mines, 1900–1936, and fluctuations in the price of copper during that period	78
5. Index map showing location of the Valdez Creek mining district	110
6. Sketch map showing location of mines and prospects in the Valdez Creek district in 1936	114
7. Sketch map of the Timberline prospects of the Alaska Exploration & Mining Co	115
8. Sketch map of the Yellowhorn prospect, Gold Hill	119
9. Index map showing location of the Fortymile, Eagle, and Circle districts	134
10. Curves showing mean precipitation, mean snowfall, and mean temperature at Eagle	141
11. Index map showing location of nickel-bearing sill on Admiralty Island	264